

AD-A273 306



1

OFFICE OF NAVAL RESEARCH

GRANT : N00014-89-J-3062

R&T Code 4132084

Technical Report No. 14

Dispersion of Rh/Cu in a Sol-Gel Matrix. Highly Chemo- and Stereoselective Catalyst for the Reduction of Alkynes to Z-Alkenes.

by

J. M. Tour, S. L. Pendalwar, C. M. Kafka, J. P. Cooper

Accepted for Publication in
Journal of Organic Chemistry

S DTIC
ELECTE
DEC 01 1993
A

Department of Chemistry and Biochemistry
University of South Carolina
Columbia, SC 29208

November 22, 1993

Reproduction in whole, or in part, is permitted for any purpose of the United States Government

This document has been approved for public release and sale; its distribution is unlimited.

93-29308



1198

93 11 30012

REPORT DOCUMENTATION PAGE			Form Approved OMB No 0704-0188	
<small>Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302 and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503</small>				
1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE 11/22/93	3. REPORT TYPE AND DATES COVERED Technical Report		
4. TITLE AND SUBTITLE Dispersion of Rh/Cu in a Sol-Gel Matrix. Highly Chemo- and Stereoselective Catalyst for the Reduction of Alkynes to Z-Alkenes.		5. FUNDING NUMBERS G- N00014-89-J3062 R&T 4132084		
6. AUTHOR(S) Tour, J. M.; Pendalwar, S. L.; Kafka, C. M.; Cooper, J. P.				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Department of Chemistry and Biochemistry University of South Carolina Columbia, SC 29208		8. PERFORMING ORGANIZATION REPORT NUMBER		
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Department of the Navy Office of Naval Research 800 North Quincy Street Arlington, VA 22217-5000		10. SPONSORING/MONITORING AGENCY REPORT NUMBER 14		
11. SUPPLEMENTARY NOTES J. Org. Chem. 1992, 57, 4786.				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Reproduction in whole or in part is permitted for any purpose of the United States Government. This document has been approved for public release and sale; its distribution is unlimited.			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) Treatment of hydrated RhCl ₃ and Cu(NO ₃) ₂ in THF and H ₂ O with triethoxysilane affords a highly chemo- and stereoselective catalyst system for the reduction of alkynes to Z-alkenes while alkyl-NO ₂ , aryl-NO ₂ , N-carbobenzyloxy, hydroxy, ester, enoate, benzyloxy, alkyl bromide, aryl bromide, and enone moieties remain unaffected.				
14. SUBJECT TERMS			15. NUMBER OF PAGES	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT Unclassified			18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	
19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified			20. LIMITATION OF ABSTRACT UL	

REVISED

**Dispersion of Rh/Cu in a Sol-Gel Matrix. Highly Chemo- and
Stereoselective Catalyst for the Reduction of Alkynes to Z-Alkenes.**

James M. Tour,* Shekhar L. Pendalwar, Cynthia M. Kafka, and Joel P. Cooper

Department of Chemistry and Biochemistry

University of South Carolina

Columbia, South Carolina 29208

Summary

Treatment of hydrated RhCl_3 and $\text{Cu}(\text{NO}_3)_2$ in THF and H_2O with triethoxysilane affords a highly chemo- and stereoselective catalyst system for the reduction of alkynes to Z-alkenes while alkyl- NO_2 , aryl- NO_2 , N-carbobenzyloxy, hydroxy, ester, enoate, benzyloxy, alkyl bromide, aryl bromide, and enone moieties remain unaffected.

Accession For		
NTIS	CRA&I	<input checked="" type="checkbox"/>
DTIC	TAB	<input type="checkbox"/>
Unannounced		<input type="checkbox"/>
Justification		
By		
Distribution /		
Availability Codes		
Dist	Avail and/or Special	
A-1		

DTIC QUALITY INSPECTED 5

Abstract

Treatment of hydrated RhCl_3 and $\text{Cu}(\text{NO}_3)_2$ in THF and H_2O with triethoxysilane affords a highly chemo- and stereoselective catalyst system for the reduction of alkynes to Z-alkenes in 6:1 to 20:1 Z:E ratios. Alkyl- NO_2 , aryl- NO_2 , N-carbobenzyloxy, hydroxy, ester, enoate, benzyloxy, alkyl bromide, aryl bromide, and enone moieties remain unaffected in the reduction process. Hydrogen is generated in situ; however, gently bubbling hydrogen gas through the system enhances the rate of the reduction. The material properties (SEM, powder XRD, surface area and specific pore volume) of the xerogel are briefly discussed.

We previously described a method for the homogeneous dispersion of 15 Å Pd(0)-particles within sol-gel matrices by the reduction of Pd(OAc)₂ with triethoxysilane in aqueous reaction mixtures with concomitant growth of the silicon oxide host.¹ The Pd-containing gels were excellent stereoselective hydrogenation catalysts for the reduction of alkynes to Z-alkenes.² Unfortunately, the chemoselectivity of the Pd-containing gel was similar to that obtained with other standard Pd-catalyst systems such as the Lindlar hydrogenation catalyst.³⁻⁵ Here we describe the use of a Rh/Cu mixed sol-gel system for the stereo- and highly chemoselective reduction of alkynes to Z-alkenes.

The reduction process involves the addition of triethoxysilane to a THF and H₂O solution of the alkyne, RhCl₃·3H₂O (1 mol%) , and Cu(NO₃)₂·2.5H₂O (15 mol %).⁶ The results of the hydrogenation reactions are summarized in Table 1. Throughout the hydrogenations, we never observed reduction or regioisomerization of the alkene. Moreover, these hydrogenation results were consistent with RhCl₃ obtained from different distributors. In an effort to further investigate the remarkable chemoselectivity, 7-dodecyn-1-ol (1) was mixed with an equimolar amount of a second unsaturated compound. Under the standard reaction conditions, none of the substrates shown in Figure 1 were reduced by the Rh/Cu catalyst system. In every case, Z-7-dodecen-1-ol was obtained in 80-99% yield in a Z:E ratio of 8:1 to 20:1.¹² Thus enones, enoates, alkyl bromides, aryl bromides, organonitro compounds, alcohols, N-cbz groups, and benzyl ethers are not reduced under the reaction conditions nor do they adversely affect the catalytic activity of this Rh/Cu system. Such a broad range of chemoselectivity in hydrogenation reactions is remarkable.³⁻⁵


The functionalities that can not be tolerated under the reaction conditions are (1) aryl iodides because they deactivate the catalyst toward reaction with an alkyne, (2) terminal alkynes which also deactivate the catalyst, (3)

Table I. Reduction of Alkynes to Z-Alkenes Using Rh/Cu Dispersed in a Sol-Gel Matrix^a

Entry	Alkyne Starting Material	Z:E Alkene Ratio ^b	% Yield ^c
1	$\text{CH}_3(\text{CH}_2)_5\text{---}\equiv\text{---}(\text{CH}_2)_5\text{CH}_3$	8:1	83
2	$\text{HO}(\text{CH}_2)_2\text{---}\equiv\text{---}(\text{CH}_2)_4\text{CH}_3$	19:1	94
3	$\text{HO}(\text{CH}_2)_6\text{---}\equiv\text{---}(\text{CH}_2)_3\text{CH}_3$ 1	17:1	98
4	$\text{CH}_3\text{O}-\overset{\text{O}}{\parallel}{\text{C}}-(\text{CH}_2)_5\text{---}\equiv\text{---}(\text{CH}_2)_3\text{CH}_3$	>20:1	84 ^d
5	$\text{PhCH}_2\text{O}-\overset{\text{O}}{\parallel}{\text{C}}-\text{NHCH}_2-\overset{\text{O}}{\parallel}{\text{C}}-\text{O}(\text{CH}_2)_6\text{---}\equiv\text{---}(\text{CH}_2)_3\text{CH}_3$	12:1	80
6	$\text{O}_2\text{N}-(\text{CH}_2)_5\text{---}\equiv\text{---}(\text{CH}_2)_3\text{CH}_3$	6:1	88

^a The reductions used 1 mol % of $\text{RhCl}_3 \cdot 3\text{H}_2\text{O}$ and 15 mol % of $\text{Cu}(\text{NO}_3)_2$ in a sol-gel matrix as described in ref 6. ^b Ratios determined by capillary GC and/or ^{13}C NMR analysis. See ref 11. ^c Isolated yields of the alkene product. ^d No exogenous H_2 source used and the reaction time was 9 h.

Figure 1

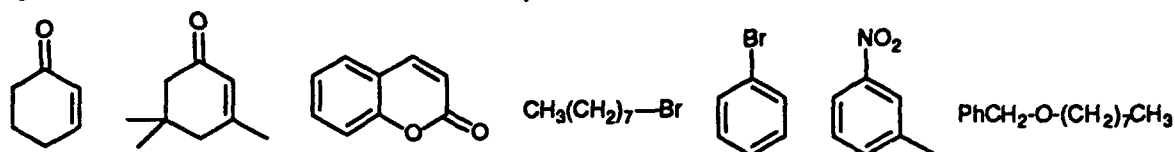

1-trimethylsilyl-1-alkynes which do not reduce cleanly to the alkene, and (4) terminal alkenes or propargylic alcohols because they undergo regioisomerization.

Several reactions conditions were studied to see the affect of using silanes in the absence of water so that no silicon sol or gel formation would occur. When the triethoxysilane reaction was executed on 7-tetradecyne (1 mol % RhCl_3 , and 15 mol % $\text{Cu}(\text{NO}_3)_2$ in THF) in the absence of water, approximately 50% of the alkyne was hydrosilylated and 35% was converted to 7-tetradecene (4.8:1 Z:E ratio) after 24 h. Then, addition of water to the reaction mixture caused protodesilylation of the

alkenyltriethoxysilane to afford a total of 71% yield of 7-tetradecene (3.5:1 *Z:E* ratio). If we used triethylsilane in place of triethoxysilane (1 mol % RhCl_3 , and 15 mol % $\text{Cu}(\text{NO}_3)_2$ in THF) in the absence of water, approximately 50% of the alkyne was hydrosilylated and 30% was converted to 7-tetradecene (3.8:1 *Z:E* ratio) after 24 h. Then, addition of water to the reaction mixture caused protodesilylation of the alkenyltriethylsilane to afford a total of 60% yield of 7-tetradecene (3.6:1 *Z:E* ratio). In the absence of triethoxysilane, a mixture of RhCl_3 and $\text{Cu}(\text{NO}_3)_2$ in THF and water does not respond as a hydrogenation catalyst with exogenous H_2 , thus, the silane is essential and the use of triethoxysilane under our standard reactions conditions proved to afford the highest yields and stereoselectivities.

We also screened other metal salts [$\text{Al}(\text{NO}_3)_3$, $\text{Ti}(\text{OEt})_4$, $\text{Zr}(\text{OEt})_4$, $\text{Zr}(\text{O})(\text{NO}_3)_2$, $\text{Ni}(\text{NO}_3)_2$, $\text{Cu}(\text{OAc})_2$, $\text{Cu}(\text{SO}_4)_2$] with RhCl_3 and noted that all of these metal salts dramatically changed the activity and the stereoselectivity of the reduction process, however, the $\text{RhCl}_3/\text{Cu}(\text{NO}_3)_2$ combination was optimal.

It is clear from powder X-ray diffraction (XRD) analysis of the xerogel (solvent free gel) that $\text{Cu}(0)$ is present in the material. However, we were not able to detect any $\text{Rh}(0)$ species even with more concentrated Rh samples; thus, we can not presently determine whether this catalyst system is homo- or heterogeneous.^{5a,13} A bimetallic system is indeed necessary since the reduction does not occur in the absence of either one of the two metals. Scanning electron micrographs (SEM) of the xerogel show only amorphous material. It was intriguing that while the Pd-containing xerogel¹ had an unusually large surface area (BET using N_2 adsorption at 77 K) of $852 \text{ m}^2/\text{g}$ and a specific pore volume (N_2 pore volume filling) of 3.33 cc/g , the Rh/Cu material had a very small surface area of only $2.8 \text{ m}^2/\text{g}$ and an undetectably low specific pore volume. Moreover, when resuspended in an aqueous THF solvent, the Rh/Cu xerogel was not an active hydrogenation catalyst in the presence of H_2 .

Acknowledgements. This research was funded by the donors of the Petroleum Research Fund, administered by the American Chemical Society, the Department of the Navy, Office of the Chief of Naval Research, Young Investigator Award Program (1989-92), the National Science Foundation (RII-8922165, DMR-9158315, DMR-9101539), and generous industrial contributors to the NSF Presidential Young Investigator Award (1991-96) for JMT: Hercules Incorporated, IBM Corporation, Ethyl Corporation, and the Shell Development Company. The SEM was purchased with a grant from the National Science Foundation (BIR-8805143).

Supplementary Material Available: Detailed reduction procedures and spectroscopic data (2 pages) for the compounds listed in Table I. Ordering information is given on any current masthead page.

References and Notes

- (1) Tour, J. M.; Pandalwar, S. L.; Cooper, J. P. *Chem. Mater.* 1990, 2, 648.
- (2) (a) Tour, J. M.; Cooper, J. P.; Pandalwar, S. L. *J. Org. Chem.* 1990, 55, 3452. (b) Tour, J. M.; Pandalwar, S. L. *Tetrahedron Lett.*, 1990, 31, 4719.
- (3) For some heterogeneous hydrogenation methods in organic synthesis, see: Rylander, P. N. "Hydrogenation Methods", Academic Press: Orlando, Florida, 1985.
- (4) For some homogeneous hydrogenation methods, see: James, B. R. "Homogeneous Hydrogenation", Wiley: New York, 1973.
- (5) For the use of other oxide-supported metal catalysts, see: (a) Lewis, L. N.; Lewis, N. *J. Am. Chem. Soc.* 1986, 108, 7228. (b) Sinfelt, J. H.; Via, G. H. *J. Catal.* 1979, 56, 1. (c) de Jongste, H. C.; Ponc, V.; Gault, F. G. *J. Catal.* 1980, 63, 395. (d) Anderson, J. R. *Structure of Metallic Catalysts*; Academic Press: New York, 1975. (e) Sinfelt, J. H. *Scientif. Amer.* 1985, 253, 90. (f) Ponc, V. *Adv. Catal.* 1983, 32, 149. (g) Sinfelt, J. H. *Bimetal. Clust. Catal.* 1977, 10, 15. (h) Biswas, J.; Bickle, G. M.; Gray, P. G.; Do, D. D.; Barbier, J. *Catal. Rev. Sci. Eng.* 1988, 30, 161. (i) Breitscheidel, B.; Zieder, J.; Schubert, U. *Chem. Mater.* 1991, 3, 559.
- (6) Triethoxysilane (2.5 mmol) was added to a solution of the alkyne (1 mmol), $\text{RhCl}_3 \cdot 3\text{H}_2\text{O}$ (0.01 mmol), and $\text{Cu}(\text{NO}_3)_2 \cdot 2.5\text{H}_2\text{O}$ (0.15 mmol), in a mixture of THF (5 mL) and H_2O (1 mL).⁷ The reaction mixture darkened and was stirred⁸ at room temperature. Molecular hydrogen was generated in situ (determined by mass spectrometry) from the hydrolysis of the Si-H linkage presumably by the known reaction of $\text{R}_3\text{Si-H}$ compounds with HOR' species in the presence of metal salts to form $\text{R}_3\text{Si-OR}'$ and H_2 .⁹ Thus, after the triethoxysilane addition, if the reaction mixture was sealed to prevent the escape of the generated H_2 , the reduction was often complete within 24 h. However, to facilitate the reduction process, exogenous H_2 was slowly bubbled through the reaction mixture and the reductions were then usually complete in 2-4 h.¹⁰ The mixture was then filtered through a 1 inch plug of silica gel

and eluted with 1:1 ether/hexane. The filtrate was dried over anhydrous sodium sulfate and concentrated. The residue was redissolved in 1:1 ether/hexane and filtered as above to afford the alkene products. Upon completion of this simple filtration process, there were no other compounds detected by capillary GC or spectroscopic analysis.

(7) Tetraethoxysilane was purchased from HULS-Petrach or Aldrich and distilled prior to use. $\text{RhCl}_3 \cdot 3\text{H}_2\text{O}$ and $\text{Cu}(\text{NO}_3)_2 \cdot 2.5\text{H}_2\text{O}$ were purchased from Alfa/Johnson Matthey and Aldrich, respectively.

(8) The reaction mixture was stirred with a magnetic stir bar and the gelation of the system is sufficiently slow so we never experienced difficulty in stirring.

(9) Sommer, L. H.; Barie, W. P., Jr.; Weyenberg, D. R. *J. Am. Chem. Soc.* 1959, 81, 251. Sommer, L. H.; Korte, W. D.; Frye, C. L. *J. Am. Chem. Soc.* 1972, 94, 3463.

(10) The H_2 (balloon) was slowly bubbled directly through the reaction mixture via a glass capillary that was drawn from a Pasteur pipet. The reactions generally took 24 h or more if they were simply placed under 1 atm of H_2 rather than having the gas bubbled through the reaction mixture. The use of higher H_2 pressures was not investigated.

(11) In most cases, the two newly formed alkenyl protons were so similar in chemical shift that routine ^1H NMR coupling constants could not be used. The stereochemical assignments were based on the ^{13}C NMR shifts of the alkenyl carbons. When alkenyl carbons are flanked by methylenes, the *Z*-alkenyl carbons are ~ 0.5 ppm further upfield than the *E*-alkenyl carbons. This trend was consistent throughout all the compounds in Table I except entry 4 where no *E*-isomer was detected. For a presentation of this trend, see: Bremser, W.; Ernst, L.; Franke, B.; Gerhards, R.; Hardt, A. "Carbon-13 NMR Spectral Data. A Living com-Microfiche Collection of Reference Material", Verlag Chemie: New York, 1979.

(12) For the unsaturated additives (1) 2-cyclohexen-1-one, (2) isophorone, (3) coumarin, (4) 1-bromooctane, (5) bromobenzene, (6) *m*-nitrotoluene, and (7) 1-benzyloxyoctane, the GC yield of the remaining unsaturated additive, the GC yield of the alkene product, and the Z:E ratio of the alkene are, respectively, (1) 95%, 99%, 10.5:1; (2) 99%, 81%, 13:1; (3) 99%, 99%, 9:1; (4) 99%, 88%, 20:1; (5) 99%, 99%, 16:1; (6) 81%, 79%, 11:1; (7) 99%, 95%, 20:1.

(13) For some work on distinguishing between heterogeneous and homogeneous reactions, see: (a) Crabtree, R. H.; Mellea, M. F.; Mihelcic, J. M.; Quirk, J. M. *J. Am. Chem. Soc.* 1982, 104, 107. (b) Lyon, D. K.; Finke, R. G. *Inorg. Chem.* 1990, 29, 1784, 1789.